



# GUIDE TO PRINTING TC POLY FILAMENTS




TCPoly has developed the first heat conducting plastics for open source FDM 3D printers. The 3D printing filaments have **thermal conductivity up to 50X higher than traditional plastics** and when combined with the design freedom of 3D printing, can be used to make high performance heat transfer products. This guide is designed to help you get the most out of the filament by enabling easier printing and better end parts.

## TCPoly Ice9 Thermally Conductive Filaments

	Flex	E-Ins	Rigid
Base Material	TPE	TPE	Nylon
Thermal Conductivity (W/m-K)	8	4	4
Max Use Temperature (°C)	110	110	175
Hardness (Shore)	Med. (90A)	Med. (95A)	High (70D)
Electrically Insulating	No	Yes	No
DI water/PEG compatible	Yes	Yes	Yes

## Optimizing your parts printing for thermal performance and speed

TCPoly materials have the highest thermal conductivity of any FDM material, but without proper print setup and slicing, the part performance can still fall short of targets. Using a combination of our design and printing expertise along with proprietary algorithms, we create toolpath commands for the highest thermal performance, print quality, and shortest print times. Contact us for more information on our slicing and print optimization services.

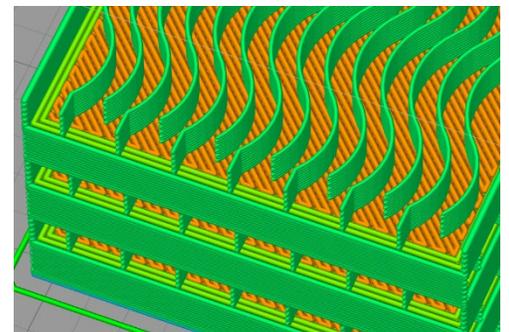



# GUIDE TO PRINTING TCPOLY FILAMENTS

## PRINT IT BIG, SLOW, AND DRY!

- **PRINT BIG:** Although you can print down to 0.4 mm, try to use a 0.8 or 1.0 mm nozzle if possible. Also use a large layer height (>50% of the nozzle diameter).
- **PRINT SLOW:** Reduce the linear print speed to get good layer adhesion and prevent nozzle buildup.  
**Note: lower linear speed does not have to be a lower print rate:** printing at 1.0/0.7 mm (nozzle/layer) at 20 mm/s is the same volumetric rate as 0.4/0.25 mm at 150 mm/s!
- **PRINT DRY:** Our filaments will absorb some moisture over time, so for the best quality prints store the material in a dry sealed container and dry at 70°C for several hours to dry out your spool. For filament drying we use the [PrintDry](#) but there are also lower cost options available, including food dehydrators on Amazon.
- **PRINT WITH RETRACTION:** Use a lot of retraction. Because Ice9 melts quickly, you need to retract it far to prevent oozing. Try 5 mm on 1.75 mm diameter, and 8 mm on 2.85 mm diameter and considering using a coast distance of 0.3-0.5 mm if available in your settings. Minimizing travel distance where possible will help too.
- **REDUCE ACCELERATION:** Fast starting and stopping will increase nozzle buildup. If you can reduce the acceleration limits on your printer, this will allow for higher linear print speeds at the same quality.
- **PRINT ON PAINTER'S TAPE:** The Ice9 Flex and E-ins filaments will adhere strongly to glass and tack print beds. To facilitate easy removal, considering printing on painter's tape. Heating the bed up to 90-110°C will also help remove the part from a bed (with or without tape). [Extra wide printers tape](#) can cover a large portion of your print bed.



0.4 and 0.8 mm nozzles


---

## PRINTERS & EXTRUDERS...

Our filament is compatible with a wide range of printers from: Ultimaker, Lulzbot, Prusa, Flash Forge, Raise 3D, Maker Gear, MakerBot, and many more.

For best results on Ice9 Flex and E-ins Ice9 we recommend printers designed for flex materials.

[Flexion](#) and [BondTech](#) extruders work very well with our entire filament catalog.

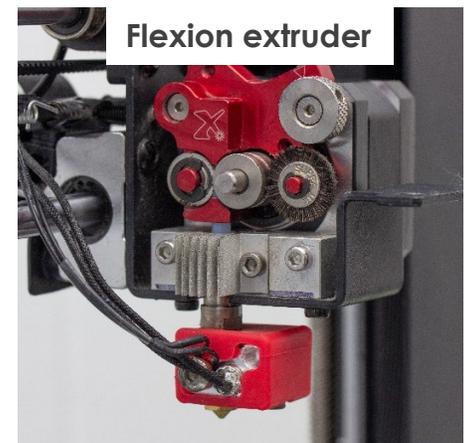

---

Find out more and order filament at [tcpoly.com/shop](https://tcpoly.com/shop)



# TROUBLESHOOTING & FAQ

---

## PROBLEM

## POSSIBLE CAUSE

## POSSIBLE SOLUTIONS

---

Inconsistent extruding

Too much resistance to flow

This can be solved by some combination of increasing the nozzle diameter and reducing the flowrate. If you are more concerned with fine detail and need a 0.4 or 0.5 mm nozzle, then consider reducing the speed to 15-20 mm/s. Otherwise move to a larger nozzle size, the material flows best at 0.6-1.0 mm nozzle diameter.

Excess moisture in filament

When the filament is left out in ambient (~20°C 50% RH) it will slowly absorb moisture and eventually become saturated. When filament saturated with moisture is melted in the hot end, the water evaporates causing the extruded filament to appear porous or bubbly. If the filament has been left out for more than a few days we recommend drying for 2-4 hours at 70°C for the highest quality prints.

Nozzle is partially clogged

Occasionally the nozzle may become partially blocked during printing. To remove the blockage we recommend running pure plastic filament through the nozzle until it runs clear with the color of the new filament. ABS or PETG work well at 240°C, but you can also use PLA if needed. If the nozzle doesn't come unclogged with this, you can use a [nozzle cleaning bit](#).

---

Unable to remove part after print

Cold adhesion too strong

The Ice9 Flex and E-ins filaments typically have very good bed adhesion, especially to glass, so we recommend printing on painters tape when possible to facilitate easy part removal. Even so, removal is best accomplished when the part is warm. Our recommended procedure is to let the part cool down to room temperature after the print, then heat the bed back up to 90°C and gently peel the painters tape off the bed and then off the bottom of the part. If not using painter's tape use a spatula to remove the part from the bed. If printing directly on glass add 10-20°C to the bed removal temperature.

---

Still can't get it to print? Contact us at [filament@tcpoly.com](mailto:filament@tcpoly.com) for additional support.



# TROUBLESHOOTING & FAQ

PROBLEM	POSSIBLE CAUSE	POSSIBLE SOLUTIONS
Poor layer adhesion	Temperature too low	Strong layer adhesion needs high enough temperature for the new layer to melt into the underlying layer. To improve layer adhesion increase the nozzle temperature by 5-10°C and also increasing the bed by 10°C.
	Nozzle too high	If the nozzle is too high in relation to the print bed, the filament will not be pushed into the previous layer creating a strong melt bond. To get the correct height relevel the print bed.
Buildup of filament on nozzle	Over extrusion	If too much material is extruded the layer height will rise and material will catch on the nozzle. Fix this by reducing the extrusion multiplier (in software) or flow (on the printer). You can also reduce the infill percentage slightly (e.g. reduce from 100 to 95%) and leave the extrusion multiplier and flow settings unchanged.
	Acceleration too high	Although TCPoly filaments can print without acceleration limits in place, reducing the max acceleration can sometimes reduce nozzle buildup since this is often caused by rapid starting and stopping. Many printers have hardware acceleration limits that can be set, we recommend limiting X and Y acceleration to 200 mm/s <sup>2</sup> if you are having issues with nozzle buildup.
Excessive oozing	Incorrect retraction settings	Thermally conductive filaments will tend to ooze more than normal filaments because the hot end melting zone will be larger. To combat this keep the retraction distance high (at least 4 mm on 1.75 mm filament and 7 mm on 2.85 mm filament) and consider using a fast retraction speed (~40 mm/s). Small coast and restart distances of 0.2-0.5 mm are also recommended. More general info on retraction <a href="#">here</a> .
	Extruder temperature too high	If adjusting the retraction settings do not improve the oozing, consider lowering the hot end temperature 10°C.

Still can't get it to print? Contact us at [filament@tcpoly.com](mailto:filament@tcpoly.com) for additional support.



# TROUBLESHOOTING & FAQ

## PROBLEM

## POSSIBLE CAUSE

## POSSIBLE SOLUTIONS

Filament kinking in extruder

Excessive resistance in hot end/nozzle

In extruders with a gap between the gear and the tube guiding the filament to the hot end, it is possible for the filament to kink and stop pushing downwards through the nozzle. This is typically caused by too great a resistance in the nozzle and can be solved by some combination of increasing nozzle diameter, increasing temperature, and reducing print speed.

Using a Bowden extruder with 1.75 mm Ice9 Flex

Our flexible filaments may not work in some Bowden style extruders due to the extra stiffness required in these systems. If the above steps to reduce resistance do not work it may be better to move to a direct extrusion printer. More info on extruder types [here](#).

Filament grinding in extruder

Extruder tension set too tight

If the filament is being chewed up by the extruder geared tooth, this usually means that the tension in the extruder is too high (i.e. there is too much pressure holding the filament against the gear). Most extruders have an adjustment so the tension can be reduced, but make sure it is not reduced so much where the filament is slipping. If this doesn't solve the problem see the explanation for excessive resistance under "Filament kinking."

Part is not air or watertight

Printing a part that seals against fluid is quite complex and requires careful setup and often post sealing. Please contact us if you are attempting to make an air or water tight part.

Part thermal performance is not good

Print oriented incorrectly

The thermal conductivity of our filament is different depending upon the print direction. Often times, reorienting the print will allow for higher thermal conductivity at a heat source and improving the performance of the part. As a rule of thumb, you would like print lines extending in the direction that you need to move heat (not perpendicular). For more indepth support on this subject, please contact us.

Still can't get it to print? Contact us at [filament@tcpoly.com](mailto:filament@tcpoly.com) for additional support.



# TROUBLESHOOTING & FAQ

---

## PROBLEM

## POSSIBLE CAUSE

## POSSIBLE SOLUTIONS

---

Part is improperly formed with too much melting

Not enough cooling between layers

For smaller parts or parts with only a few features at certain heights, it may take more time for a layer to cool than is proscribed in the standard print settings. You can use standard print settings to reduce speed and increase cooling in these areas. Typical settings involve decreasing a print speed or increasing a fan speed if a layer print time is below a certain value (e.g. 15 sec.). If these settings doing work or aren't available try enabling the cooling fan for all layers after the first (for a small part) or just for the fine features.

---

Poor bed adhesion

Nozzle too high/first layer too fast

The Ice9 Flex and E-ins filaments typically have very good bed adhesion, so the culprits for poor bed adhesion will be common to general FDM printing. Ensure that the bed is level and the first layer is printed slower with the nozzle closer to the bed if you are having issues. We typically recommend first layer speed ~60% of the print speed in subsequent layers and having the nozzle 25% closer on the first layer if possible. More general info [here](#).

---

Nozzle clogged

Occasionally the nozzle may become partially blocked during printing. To remove the blockage we recommend running pure plastic filament through the nozzle until it runs clear with the color of the new filament. ABS or PETG work well at 240°C, but you can also use PLA if needed. If the nozzle doesn't come unclogged with this, you can use a [nozzle cleaning bit](#).